


Direct Tension Test - A Useful Tool in Evaluation of Polymer Modified Asphalt

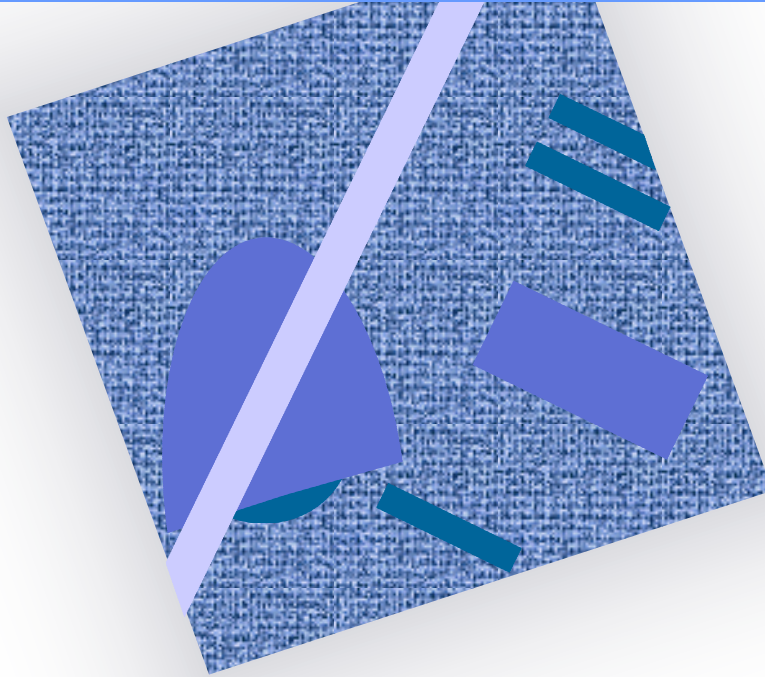

**Susanna Ho and
Ludo Zanzotto**
Bituminous Materials Chair
University of Calgary

**The 2nd International Symposium on Binder Rheology
and Pavement Performance**
September 9-11, 2001, Philadelphia, PA.

11/4/2001



**UNIVERSITY OF
CALGARY**

Outline

- Literature Background - The Low-temperature Performance of Asphalt Binder upon Polymer Modification
- Experimental Method
- Polymer Modified Asphalts for Colder Climates
- Polymer Modified Asphalts for Warmer Climates
- Polymer Modified Asphalts Black Max™
- Summary and Conclusions



UNIVERSITY OF
CALGARY

Literature Background

- The improvement of the performance of PMAs at low service temperature has been controversial.
- It was suggested that the presence of polymer allows the use of softer base asphalts - “sponge” theory
- Based on AASHTO MP1 using the BBR, the stiffness of the base asphalt either increases, remains unchanged or very marginally decreases upon polymer modification.
- An AASHTO MP1A method was developed.

Experimental Method

- The direct tension test (DTT) and the new parameter T_{critical} were used to study the low-temperature behavior of selected groups of PMA.
- Three groups of PMA were studied -
 - PMA's for colder climates
 - PMA's for warmer climates(Laboratory prepared using two types of polymer)
 - Three grades of Black MaxTM - commercial products of Husky Energy
- The sample preparation technique of DTT was developed at the University of Calgary

PMAs for Colder Climates

- The levels of polymer modification in this group of three PMAs were 1.0s, 1.5s and 2.5s where “s” is a unit of polymer.
- All three materials were tested according to the Superpave specification, including DTT and T_{critical} .
- An asphalt from Husky Energy was used as the base asphalt.

Level of Polymer Modification	1.0s	1.5s	2.5s
<u>STANDARD TESTS</u>			
Penetration at 25 °C, [dmm] (100g/5s)	175	159	120
Softening Point, [°C]	45.8	52.2	68.8

SUPERPAVE TESTS

Original Binder Properties

Viscosity at 135 °C, [mPa.s]	443	585	1411
Dynamic Shear ($G^*/\sin \delta$), (Min. 1.0 kPa), [kPa]	1.14	1.03	1.03
Temperature, [°C]	60	64	75

RTFOT (T240)

RTFOT Mass Loss, [%]	-0.692	-0.636	-0.710
Dynamic Shear ($G^*/\sin \delta$), (Min. 2.20 kPa), [kPa]	2.30	2.28	2.21
Temperature, [°C]	61	63	73

Pressure Aging Vessel Residue

PAV Aging Temperature, [°C]	100	100	100
Dynamic Shear [$G^*(\sin \delta)$], (Max. 5000 KPa), [kPa]	2271	2068	808
Temperature, [°C]	16	16	22

PMA for Colder Climates

Level of Polymer Modification	1.0s		1.5s		2.5s	
Creep Stiffness (S - max. 300 MPa) @ 60 s	276		291		267	
(m value - min. 0.300) @ 60 s	0.312		0.315		0.319	
Temperature, [°C]	-26.0		-28.0		-28.0	
MP1 Actual Grading	PG60-36		PG63-38		PG73-38	
MP1 ΔT	96		101		111	
MP1 Superpave Grading	PG58-34		PG58-34		PG70-34	
Direct Tension Failure Strain [%]	1.12	1.65	1.56	2.90	1.34	2.92
Direct Tension Failure Stress [MPa]	6.66	6.46	7.38	7.11	8.99	7.43
Direct Tension Test Temperature [°C]	-30.0	-27.0	-30.0	-27.0	-34.0	-28.0
T _{critical} [°C]	-38.0		-39.4		-42.2	
T _{critical} vs. T _{s,m} [°C]	-2.0		-1.4		-4.2	
MP1A Actual Grading	PG60-38		PG63-39		PG73-42	
MP1A ΔT	98		102		115	
MP1A Superpave Grading	PG58-34		PG58-34		PG70-40	


PMAs for Colder Climates

<u>Level of Modification</u>	<u>1.0s</u>	<u>1.5s</u>	<u>2.5s</u>
DT test temp. at 2.0% failure strain[°C]	-25	-28.5	-30.5
Failure stress at 2.0% failure strain [MPa]	6.2	7.2	8.2
DT test temp. at 1.3% failure strain[°C]	-29	-31	-33
Failure stress at 1.3% failure strain [MPa]	6.5	7.5	9.0



UNIVERSITY OF
CALGARY

Figure 1. Thermal Stress versus Temperature – PMAs for Colder Climates

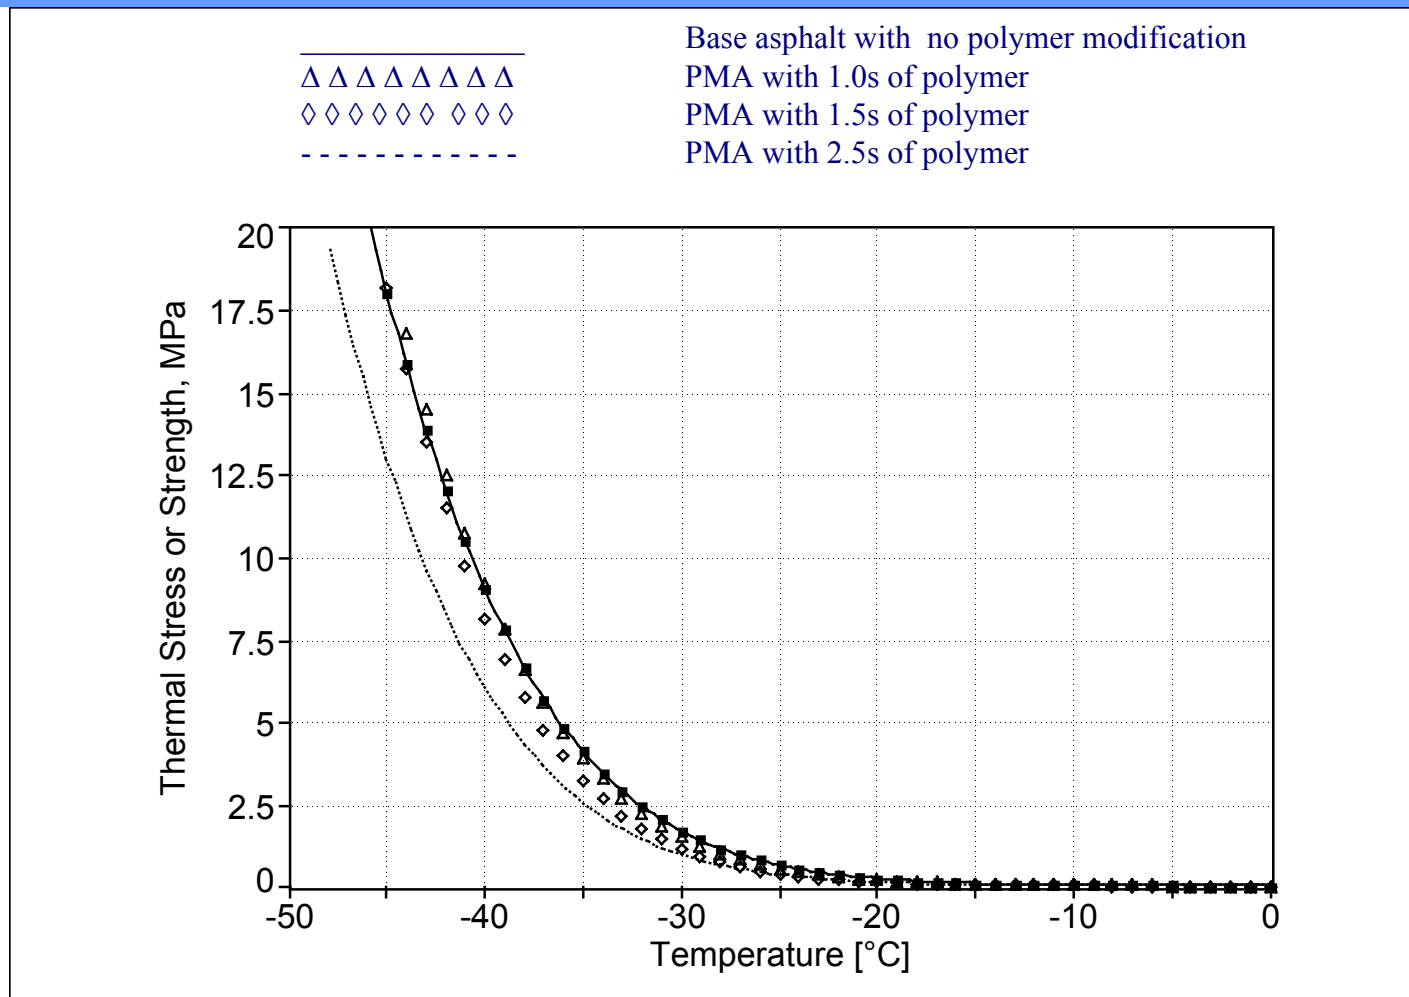

Impact of Polymer

The impact of polymer on the low-temperature performance of asphalt binder (except the indirect one that allows the use of softer base asphalt) can be at least two fold -

- Increase the tensile strength of the binder
- Decrease the thermal stress induced by the decreasing temperature



UNIVERSITY OF
CALGARY

PMAs for Warmer Climates

- The level of polymer modification in this group of three PMAs were 1.5x, 2.0x and 2.5x where “x” is a unit of polymer.
- All three materials were tested according to the Superpave specification, including DTT and T_{critical} .
- A different asphalt from Husky Energy was used as the base asphalt.

Level of Polymer Modification	1.5x	2.0x	2.5x
<u>STANDARD TESTS</u>			
Penetration at 25 °C, [dmm] (100g/5s)	74	76	67
Softening Point, [°C]	54.8	57.7	60.9

SHRP TESTS

Original Binder Properties

Viscosity at 135 °C, [mPa.s]	983	1169	1601
Dynamic Shear ($G^*/\sin \delta$), (Min. 1.0 kPa), [kPa]	1.10	1.16	1.11
Temperature, [°C]	73	74	78

RTFOT (T240)


RTFOT Mass Loss, [%]	-0.268	-0.390	-0.255
Dynamic Shear ($G^*/\sin \delta$), (Min. 2.20 kPa), [kPa]	2.27	2.31	2.3
Temperature, [°C]	71	73	76

Pressure Aging Vessel Residue

PAV Aging Temperature, [°C]	100	100	100
Dynamic Shear [$G^*(\sin \delta)$], (Max. 5000 kPa), [kPa]	1980	2118	1200
Temperature, [°C]	25	25	28

Level of Polymer Modification	1.5x		2.0x		2.5x	
Creep Stiffness (S - max. 300 MPa) @ 60 s	272		255		258	
(m value - min. 0.300) @ 60 s	0.302		0.297		0.290	
Temperature, [°C]	-20.0		-21.0		-21.0	
MP1 Actual Grading	PG71-30		PG73-30		PG76-30	
MP1 ΔT	101		103		106	
MP1 Superpave Grading	PG70-28		PG70-28		PG76-28	
Direct Tension Failure Strain [%]	1.17	2.11	1.75	2.14	1.39	1.75 2.17
Direct Tension Failure Stress [MPa]	6.47	6.21	7.57	6.71	9.85	8.35 7.86
Direct Tension Test Temperature [°C]	-24.0	-20.0	-24.0	-22.0	-30.0	-26.0 -24.0
T _{critical} [°C]	-31.8		-33.7		-34.1	
T _{critical} vs. T _{s,m} [°C]	-1.8		-3.7		-4.1	
MP1A Actual Grading	PG71-31		PG73-33		PG76-34	
MP1A ΔT	102		106		110	
MP1A Superpave Grading	PG70-28		PG70-28		PG76-34	

Figure 3. Failure Stress versus Test Temperature in DTT for PMAs for Warmer Climates

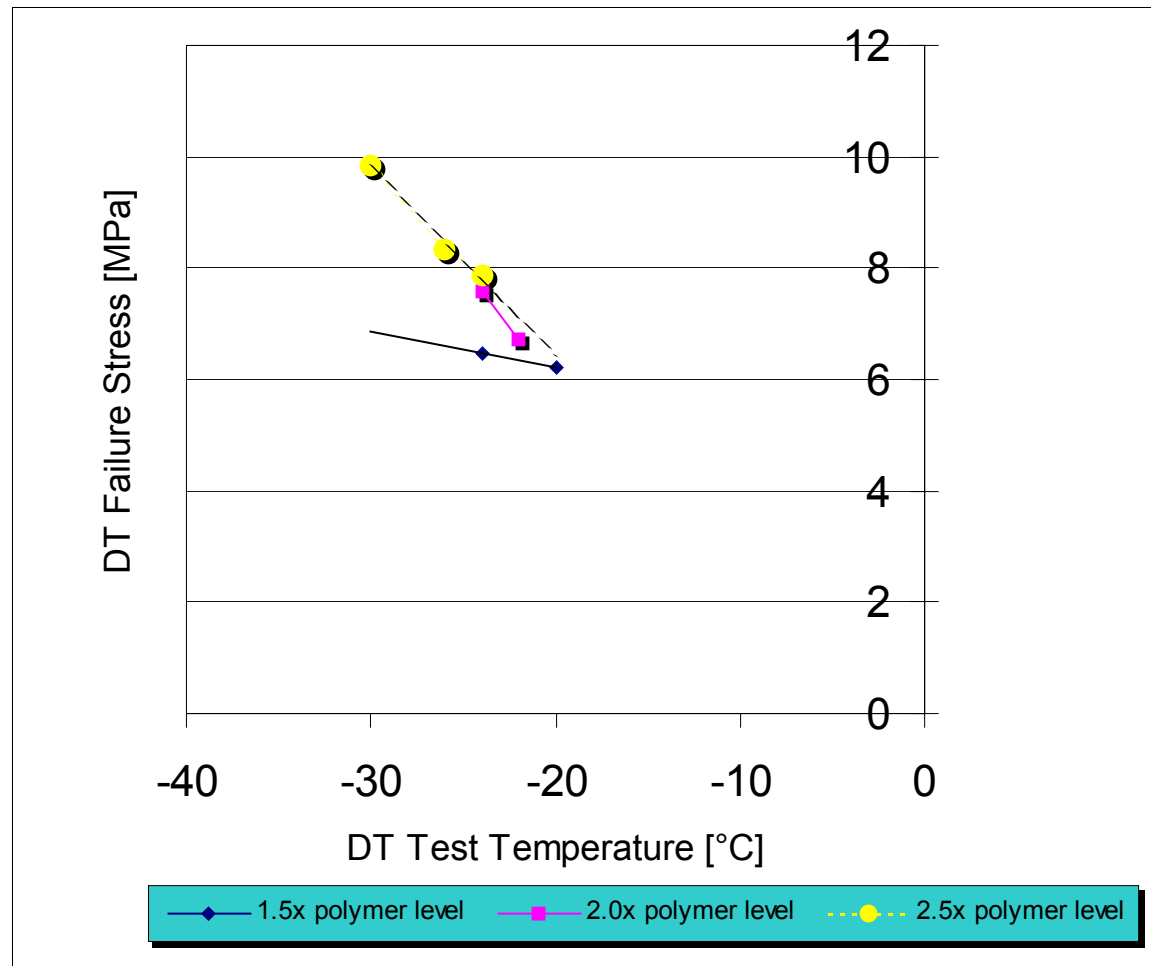


PMA for Warmer Climates

<u>Level of Modification</u>	<u>1.5x</u>	<u>2.0x</u>	<u>2.5x</u>
DT test temp. at 2.0% failure strain[°C]	-20	-22	-24
Failure stress at 2.0% failure strain [MPa]	6.2	6.7	7.9
DT test temp. at 1.75% failure strain[°C]	-22	-24	-26
Failure stress at 1.75% failure strain [MPa]	6.4	7.6	8.4

If 1.3% DT failure strain were used as a criterion for passing a certain grade, the PMA with 2.5x level of polymer modification would have passed -40.0°C for the low-temperature grading.

Figure 2. Thermal Stress versus Temperature – PMAs for Warmer Climates

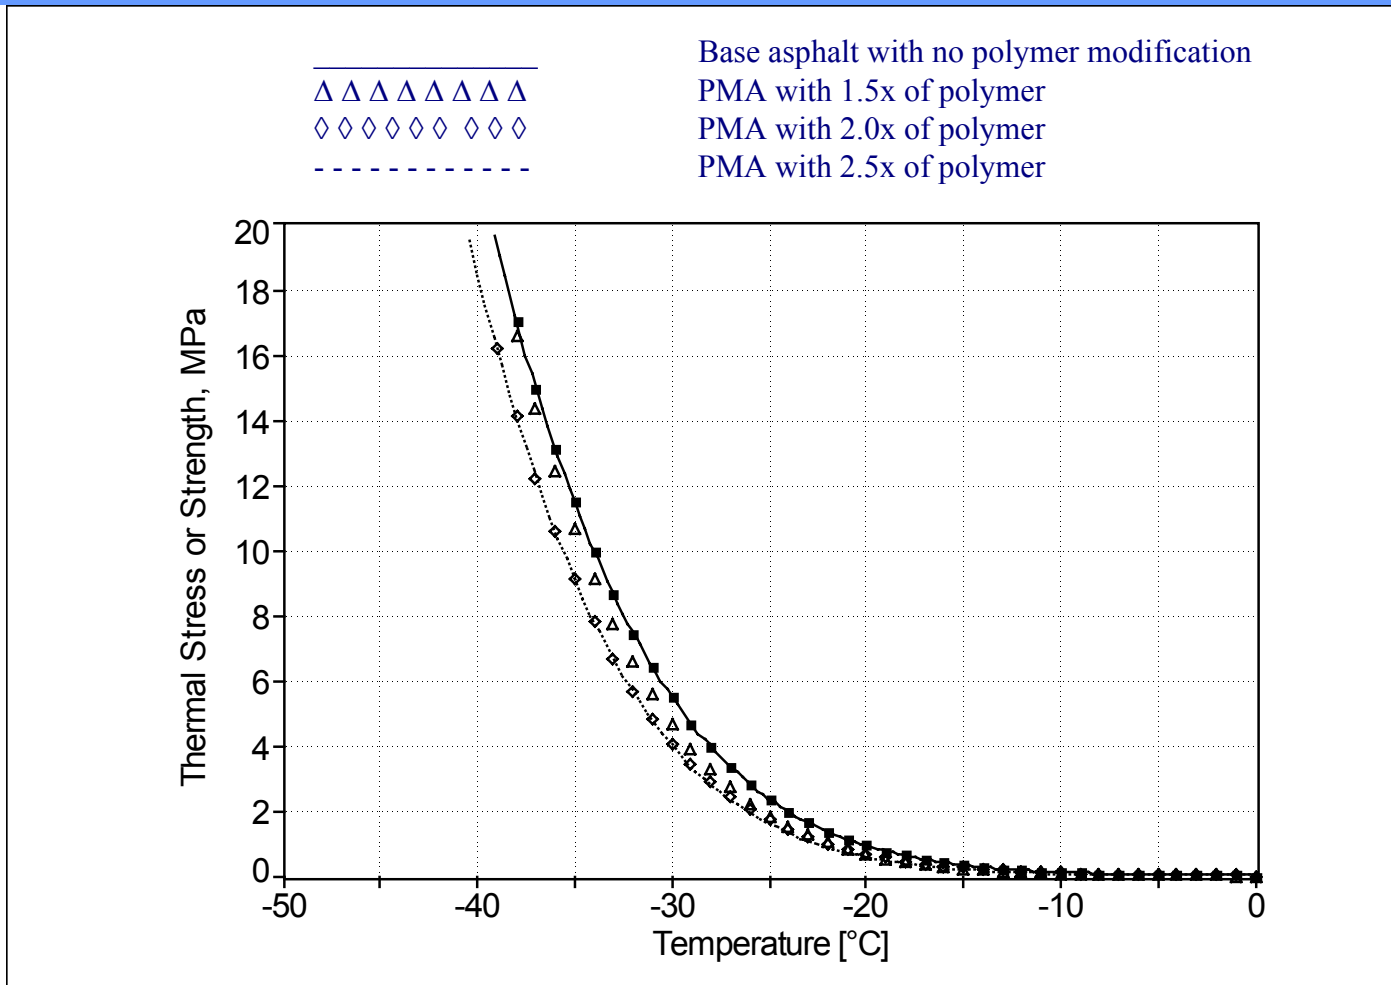

Questions to be answered -

The following questions should be answered by future studies :

- Should the inclusion of failure strain values in DTT evaluation of asphalt materials be reconsidered?
- Should the stiffness and m-value from BBR be excluded as the low temperature parameter for evaluation of asphalt binder, especially the PMAs?

Polymer Modified Asphalts Black Max™

- Three commercially available Black Max™ PMAs produced by Husky Energy were also studied.
- All three materials were tested according to the Superpave specification, including DTT and $T_{critical}$.



UNIVERSITY OF
CALGARY


Husky PMA	Black Max™ I	Black Max™ II	Black Max™ III
Dynamic Shear ($G^*/\sin \delta$), (Min. 1.0 kPa), [kPa]	1.02	1.01	1.01
Temperature, [°C]	62	70	75
RTFOT (T240)			
Dynamic Shear ($G^*/\sin \delta$), (Min. 2.20 kPa), [kPa]	2.27	2.46	2.27
Temperature, [°C]	62	68	75
Pressure Aging Vessel Residue			
PAV Aging Temperature, [°C]	100	100	100
Dynamic Shear [$G^*(\sin \delta)$], (Max. 5000 KPa),[kPa]	4180	1459	1303
Temperature, [°C]	7	19	22

Husky PMA

Black Max™ I Black Max™ II Black Max™ III


Creep Stiffness (S - max. 300 MPa) @ 60 s	296	255	198
(m value - min. 0.300) @ 60 s	0.319	0.302	0.308
Temperature, [°C]	-30.0	-27.0	-24.0
MP1 Actual Grading	PG62-40	PG68-37	PG75-34
MP1 ΔT	102	105	109
MP1 Superpave Grading	PG58-40	PG64-34	PG70-34
Direct Tension Failure Strain [%]	1.36 2.97	1.27 2.01	1.61 2.60 3.60
Direct Tension Failure Stress [MPa]	8.25 7.25	8.53 8.04	9.65 7.79 7.28
Direct Tension Test Temperature [°C]	-35.0 -30.0	-34.0 -30.0	-34.0 -29.0 -28.0
T _{critical} [°C]	-43.2	-41.3	-40.3
T _{critical} vs. T _{s,m} [°C]	-3.2	-4.3	-6.3
MP1A Actual Grading	PG62-43	PG68-41	PG75-40
MP1A ΔT	105	109	115
MP1A Superpave Grading	PG58-40	PG64-40	PG70-40

Figure 4. DT Failure Stress – Strain Curve of Black Max™ III Tested at -34.0°C

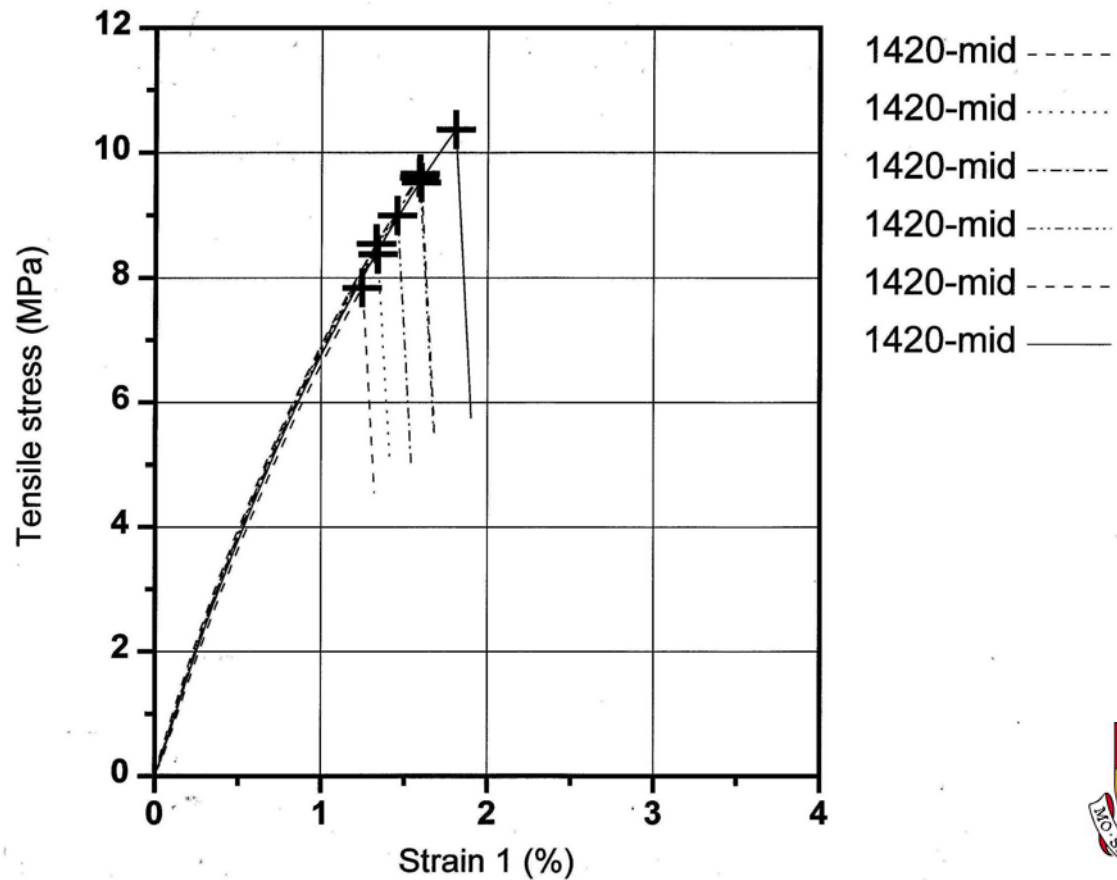

UNIVERSITY OF
CALGARY

Figure 5. Fracture Strength and Thermal Stress Curve of Black Max™ III with a Linear Fit

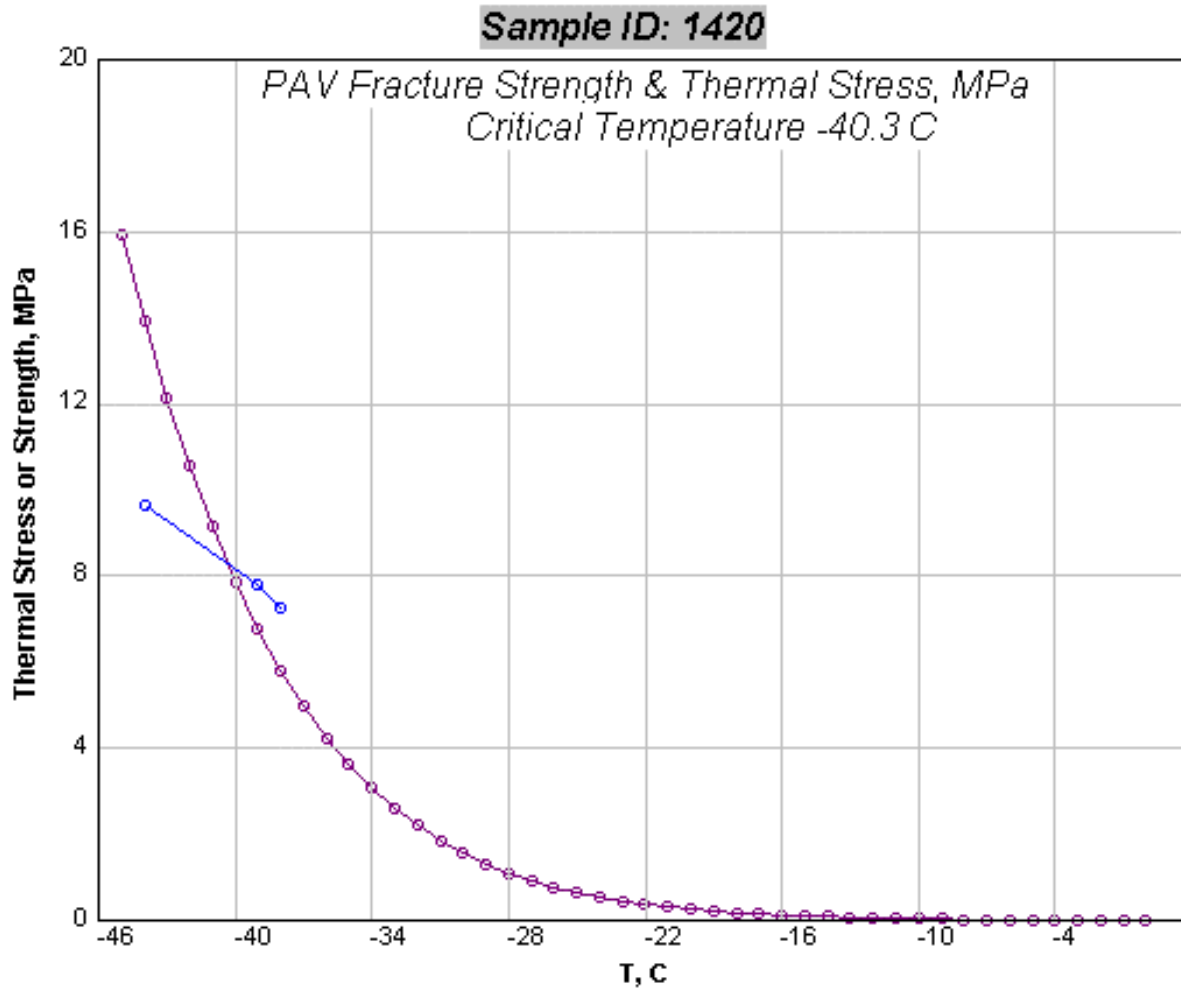

Summary and Conclusions

Test Methodology

- The MP1 passing temperature parameter was not able to differentiate between the low-temperature performances of different PMAs. The passing temperature based on stiffness and m-value should be questioned.
- The T_{critical} was able to differentiate among the low temperature performance of different PMAs and to recognize the increasing amount of polymer in PMA.
- The data obtained from DTT can be used for deeper analysis of the low-temperature behavior of asphalt binders. The failure strain might be utilized to obtain a better understanding of the low-temperature behavior.

Summary and Conclusions

Character of Polymer Modified Asphalt

- We used to think that the positive impact of polymers on the low-temperature performance of PMAs to be only indirect - allowing the use of softer base asphalt. The MP1 passing temperature parameter showed that increased amount of polymer in PMA in most cases increased the stiffness and decreased the m-value.
- The analysis of data from DTT and BBR as performed by TSAR™ indicated that the improvement of the low temperature performance of asphalt modified by polymers can actually be threefold -

Three Fold Impact of Polymer in PMA

- Indirect improvement by allowing the use of softer asphalt base as recognized previously.
- Improvement caused by the increase in the DTT failure stress of asphalt binder by increasing the amount of polymer.
- Improvement caused by the decrease in the thermal stress in the asphalt binder by increasing amount of polymer.



UNIVERSITY OF
CALGARY

Acknowledgment

The authors wish to express their gratitude to
Husky Energy and
the Natural Sciences and Engineering
Council of Canada
for the financial support of this project.



UNIVERSITY OF
CALGARY